

TEST REPORT


Report No. : MAN:TR:9530018459

DATE : 20/10/2018



OPTIKS KARKHANA INDIA PRIVATE LIMITED
 C-3/303, OLIVE COUNTY SECTOR-5, VASUNDHARA
 GHAZIABAD-201012
 IN

CONTACT PERSON : MR. PRADYUMNA SHANDILYA
THE FOLLOWING SAMPLE(S) WAS/WERE SUBMITTED AND IDENTIFIED BY/ON BEHALF OF THE CUSTOMER AS :
SAMPLE DESCRIPTION BAYER 2407 POLYCARBONATE
COUNTRY OF ORIGIN INDIA
SAMPLE RECD ON 11/10/2018 **TESTING PERIOD :** 17/10/2018 - 17/10/2018
TEST(S) REQUESTED MVR/MFR TEST

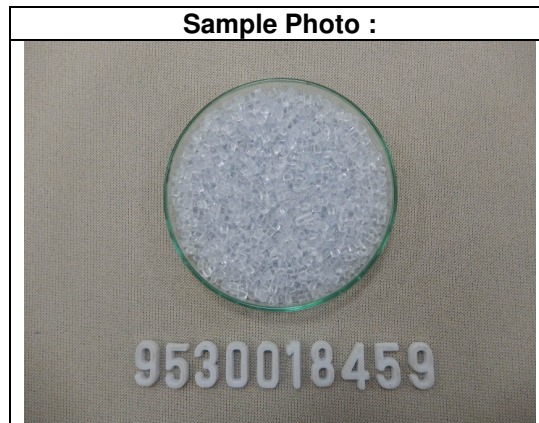

MVR/MFR TEST:

Test method : ISO 1133-1 : 2011, (Procedure-B)

Test condition : Pre-dried at 90°C for 3 hrs.

Test conducted at 300°C & 1.2 kg load.

Observation :

| S No | MFR (melt flow rate) (g/10min) | MVR (melt volume rate) (cm ³ /10min) |
|-------------|--------------------------------------|---|
| 1 | 21.08 | 21.45 |
| 2 | 20.05 | 20.06 |
| 3 | 21.23 | 20.19 |
| Mean | 20.79 | 20.56 |

TEST REPORT

Report No. : MAN:TR:9530018459

DATE : 20/10/2018



Note : Test performed as per the conditions given by the client.
Above test has been subcontracted to **SGS approved lab.**

***** End of Report*****

Per Pro SGS India Private Ltd

Authorized Signatory

Lalit Raheja
(Asst. Manager)

Email your Test Report Related Enquiries at Feedback.TRP@sgs.com